


## Band Structure of Graphene

Graphene is a single <sup>2D</sup> layer of graphite, consisting of carbon atoms arranged in a honeycomb structure.


honeycomb structure: underlying triangular BL with two point basis

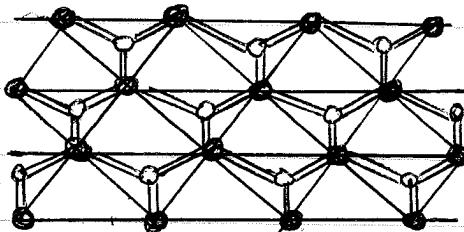

Denote  
 • as "A" sites  
 ○ as "B" sites

A sites sit on the sites  $\vec{R}$  of the underlying triangular lattice.

B sites sit at sites  $\vec{R} + \vec{d}$



primitive vectors of the BL


$$\left\{ \begin{array}{l} \vec{a}_1 = a \hat{x} \\ \vec{a}_2 = \frac{a}{2} \hat{x} + \frac{\sqrt{3}}{2} a \hat{y} \end{array} \right.$$

basis vectors

$$\left\{ \begin{array}{l} \vec{0} \\ \vec{d} = \frac{1}{3} (\vec{a}_2 + (\vec{a}_2 - \vec{a}_1)) \\ = \frac{a}{\sqrt{3}} \hat{y} \end{array} \right.$$

primitive vectors of R-L.

$$\left\{ \begin{array}{l} \vec{b}_1 = \frac{2\pi}{a} \hat{x} - \frac{2\pi}{\sqrt{3}a} \hat{y} \\ \vec{b}_2 = \frac{4\pi}{\sqrt{3}a} \hat{y} \end{array} \right.$$

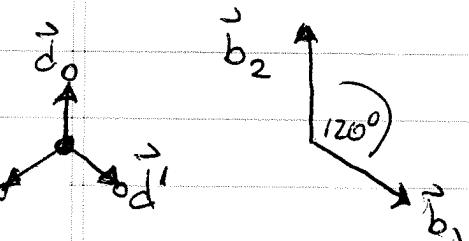

nearest neighbors of A site are displaced from A by vectors

$$\vec{d}, \vec{d}' = (\vec{a}_1 - \vec{a}_2) + \vec{d} = \frac{a}{2} \hat{x} - \frac{a}{2\sqrt{3}} \hat{y}, \vec{d}'' = -\vec{a}_2 + \vec{d} = -\frac{a}{2} \hat{x} - \frac{a}{2\sqrt{3}} \hat{y}$$

Atomic Carbon has electron structure

$\uparrow \downarrow$     $\uparrow \downarrow$     $\uparrow \uparrow$

$1s^2$     $2s^2$     $2p^2$


6 electrons

4 electrons in outermost  
 $n=2$  shell.

The  $1s^2$  electrons have significantly lower energy than the  $n=2$  electrons. When C is in the honeycomb structure, they remain tightly bound to the C ion and do not participate in bonding or conduction. We thus forget about them!

The  $2s^2$  and  $2p^2$  electrons are very close in energy. When C is placed in the honeycomb structure, these atomic orbitals will mix ("hybridize").

The  $n=2$  orbitals are

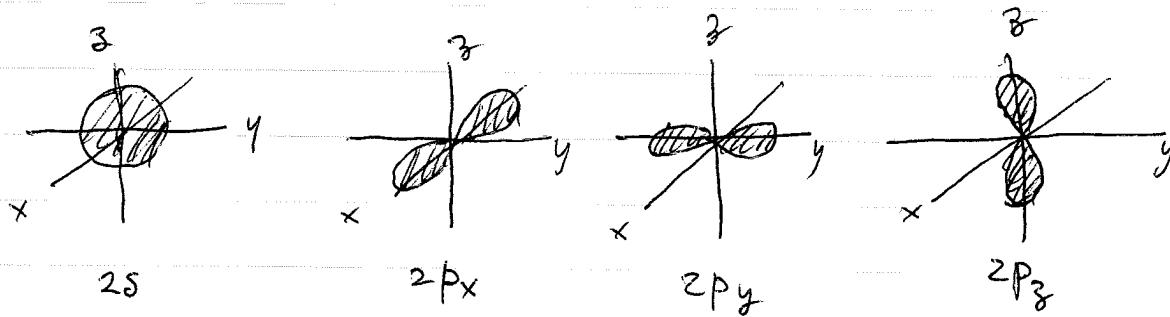

$2s$  is spherically symmetric

$2p$  has lobes oriented along  $\hat{x}$ ,  $\hat{y}$ , and  $\hat{z}$  axes

honeycomb structure we take to be in the  $xy$  plane

If one does a tight binding calculation of the band structure from the  $n=2$  shell electrons, one should mix in all  $2s$ ,  $2p_x$ ,  $2p_y$ ,  $2p_z$  orbitals.

Since there are two atoms per primitive cell of the BL (since it is BL with two-point basis) and there are four atomic orbitals to consider, the Bloch wavefunction is a mixture of 8 terms:


$$\psi_{\vec{k}} = \sum_{\vec{R}} e^{i\vec{k} \cdot \vec{R}} \left\{ b_{AS} \varphi_{AS} + b_{AP_x} \varphi_{AP_x} + b_{AP_y} \varphi_{AP_y} + b_{AP_z} \varphi_{AP_z} \right. \\ \left. + b_{BS} \varphi_{BS} + b_{BP_x} \varphi_{BP_x} + b_{BP_y} \varphi_{BP_y} + b_{BP_z} \varphi_{BP_z} \right\}$$

where  $\varphi_{AS}$ ,  $\varphi_{AP_x}$  etc are the s,  $p_x$ , etc atomic orbital wavefunctions centered at sites "A", and  $\varphi_{BS}$ ,  $\varphi_{BP_x}$  etc are the s,  $p_x$ , etc atomic orbital wavefunctions centered at sites "B".

For each value  $\vec{k}$  in 1<sup>st</sup> BZ one then get eight energies  $E_n(\vec{k})$ , i.e. 8 bands,


Digression: For C in a 3D diamond structure (fcc with 2-point basis) one finds that the s,  $p_x$ ,  $p_y$ , and  $p_z$  orbitals all mix together ~~to~~ roughly equally - this is called " $sp^3$ " hybridization since one s mixes with three p orbitals. The 8 bands separate into two distinct groups: the lowest four bands are called " $\sigma$ -bonding" bands. Here the

wavefunctions from the A and B sites add roughly symmetrically so that the electron probability density is concentrated midway between A and B atoms. These form  $\sigma$ -bonding bands give Bloch electron wavefunctions where the electron density is concentrated on the nearest neighbor bonds of the diamond structure. These are the covalent bonds that hold the diamond structure together. The higher four bands are called " $\sigma^*$ -antibonding" bands. Here the A and B site wavefunctions add roughly antisymmetrically so that the electron probability vanishes midway between A and B. The  $\sigma^*$ -antibonding bands lie higher in energy than the  $\sigma$ -bonding bands and do not overlap them. In the ground state, each ~~con~~ of the two ions in a primitive cell of the BL give 4 electrons, for a total of 8 electrons per BL cell. These 8 electrons fill up the 4  $\sigma$ -bonding bands (each band can hold 2 electrons per ion - since each  $k$  can have spin  $\uparrow$  and spin  $\downarrow$ ) Hence the 4  $\sigma$ -bonding bands are completely filled and the 4  $\sigma^*$ -antibonding bands are completely empty. There is a finite energy gap between the  $\sigma$  and  $\sigma^*$  bands  $\Rightarrow$  diamond is an insulator

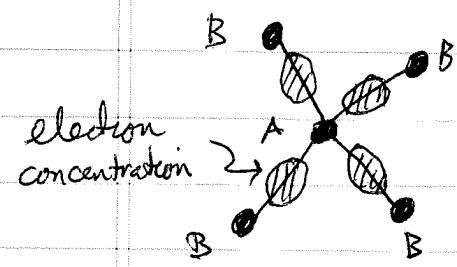

the 4 nearest neighbors of an A site are the equidistant B sites that lie at the vertices of a regular tetrahedron. The  $\sigma$ -bonding states concentrate electron density along bonds connecting nearest neighbors

# Covalent Bonding: Hybrid Orbitals

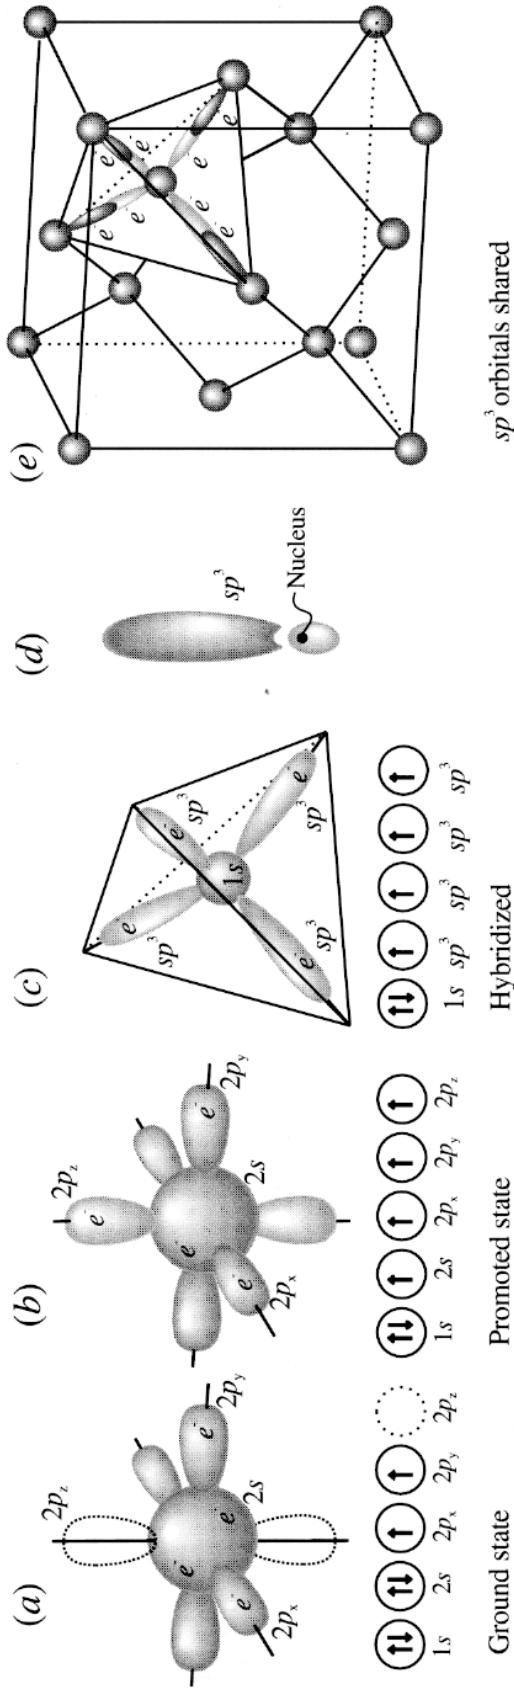


**Figure 3.5** Formation of covalent sigma ( $\sigma$ ) bonds with carbon in diamond. (a) Ground-state electron configuration of carbon. The  $2s$  orbital contains two electrons, the  $2p_x$  and  $2p_y$  orbitals each contain one electron, and the  $2p_z$  orbital is vacant. (b) One electron from the  $2s$  orbital is promoted to the  $2p_z$  orbital so that four orbitals are partially filled. (c) Hybridization of the half-filled orbitals into four identical  $sp^3$  orbitals arrays to point to the corners of a tetrahedron. (d) Each  $sp^3$  orbital consists of a large lobe and a small lobe on the opposite sides of the nucleus. The small lobes are not shown in (c). (e) Bonding of carbon atoms in diamond by sharing electrons between hybridized  $2sp^3$  orbitals on adjacent atoms. Four pairs of overlapping  $sp^3$  orbitals reaching a carbon atom are shown; similar bonds occur along each of the solid lines. The small lobes are omitted for clarity.

Diamond Example - Pure Carbon in complex 3D network

Graphene: For C in a 2D honeycomb structure one finds that the  $s$ ,  $p_x$ , and  $p_y$  orbitals all mix together roughly equally (these are the orbitals which have significant electron probability in the  $xy$  plane) - while the  $p_z$  orbital remains separated. The  $s-p_x-p_y$  mixed states are called " $sp^2$ " hybridization as one  $s$  mixes with two  $p$  orbitals.

The  $sp^2$  states give rise to 3  $\sigma$ -bonding bands and 3  $\sigma^*$ -antibonding bands. The  $p_z$  states give rise to two bands - the  $\pi$ -band and the  $\pi^*$ -band. (so we have a total of 8 bands)

The  $\sigma$ -bonding bands give wavefunctions with electron concentration along the free nearest neighbor bonds between A and B sites in the  $xy$  plane. These are the covalent bonds that hold the honeycomb structure together.

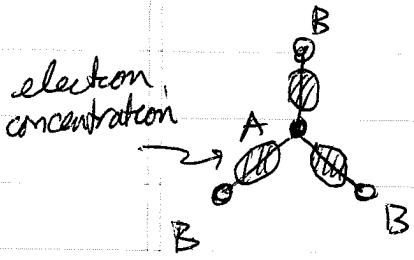

The  $\sigma$ -bonding bands have the lowest energy and all lie ~~below~~ below the Fermi energy. In the ground state they are completely filled taking 6 of the 8 electrons per  $B_2$  cell. Since these bands are filled, they play no role in electric conduction in graphene.


The  $\sigma^*$ -anti bonding bands all lie above the Fermi energy. In the ground state they are completely empty, hence we ignore them. (There is a finite energy gap between the min energy of the  $\sigma^*$  bands and the Fermi energy)

All the interesting effects concerning conduction therefore lie with the  $\pi$  and  $\pi^*$  bands.


These lie essentially between the  $\sigma$  and  $\sigma^*$  bands (though actually the  $\sigma$  band near its max overlaps some with the min of the  $\pi$  band, and the max of the  $\pi^*$  band overlaps somewhat with the min of the  $\sigma^*$  band. But these overlapping regions lie well below or well above, respectively, the Fermi energy and so play no role in conduction — conduction is determined by electrons in close vicinity of the Fermi energy only!)

We will soon see that the  $\pi$  and  $\pi^*$  bands do not overlap. Therefore in the ground state, with 8 electrons per BL cell, 6 electrons go to completely filling the 3  $\sigma$  bands, and 2 electrons go to completely filling the  $\pi$  band. The  $\pi^*$  and  $\sigma^*$  bands are completely empty. This would be an insulator except we will see that the  $\pi$  and  $\pi^*$  bands


# Covalent Bonding: Sigma vs. Pi bonds

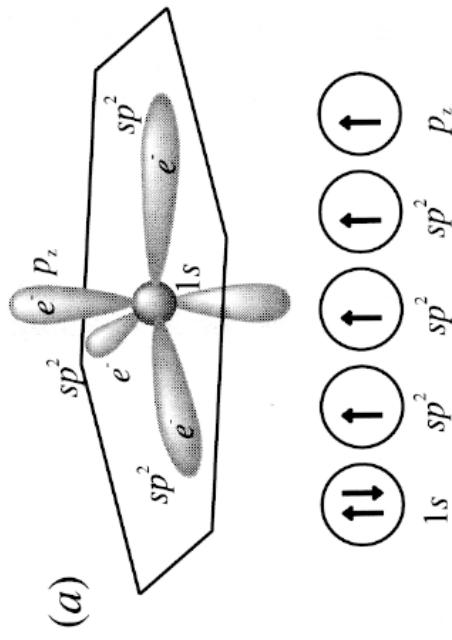

(b)

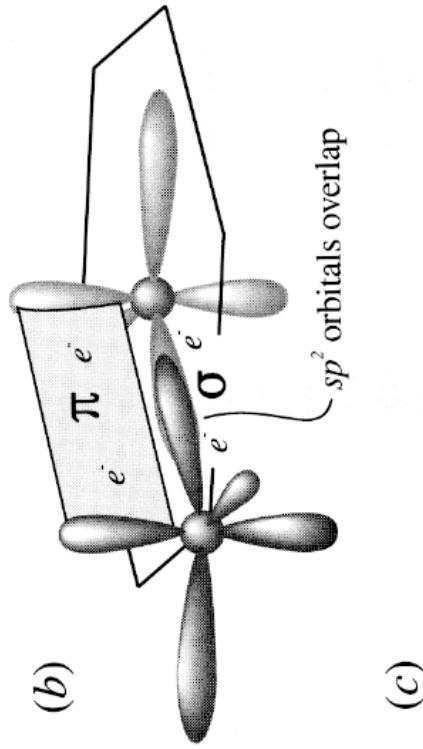

(c)

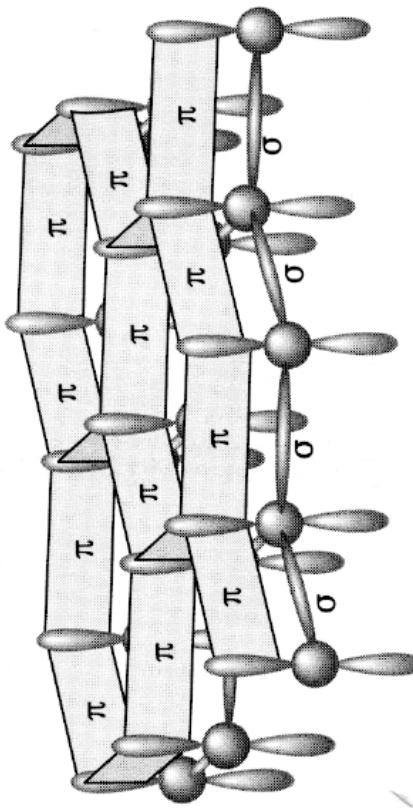

Note the hexagonal symmetry  
and that graphite tends to form  
in layered sheets

pi bonds are weaker than sigma bonds

Graphite Example - Pure Carbon in layered 3D network

are degenerate (no energy gap) at the Fermi surface.

We therefore will do a tight binding calculation involving only the  $p_z$  orbital alone as a rough calculation for the  $\Pi$  and  $\Pi^*$  bands.

Let  $\begin{cases} \varphi_A(\vec{r}) \equiv \varphi(\vec{r}) & p_z \text{ orbital centered at origin (site A)} \\ \varphi_B(\vec{r}) \equiv \varphi(\vec{r}-\vec{d}) & p_z \text{ orbital centered at position } \vec{d} \text{ (site B)} \end{cases}$

Our assumed Bloch wavefunction then has the form:

$$\psi_k(\vec{r}) = \sum_{\vec{R}} e^{i\vec{k} \cdot \vec{R}} \{ b_A \varphi_A(\vec{r}-\vec{R}) + b_B \varphi_B(\vec{r}-\vec{R}) \}$$

Consider

$$\vec{k} \in 1^{\text{st}} \text{ BZ}$$

$$\langle \varphi_A | H | \psi_k \rangle = \langle \varphi_A | \text{H} \text{at} + \Delta U | \psi_k \rangle$$

!!

$$\epsilon_k \langle \varphi_A | \psi_k \rangle = E \langle \varphi_A | \psi_k \rangle + \langle \varphi_A | \Delta U | \psi_k \rangle$$

$\uparrow$

energy of atomic  $p_z$  orbital

$$\langle \varphi_A | \psi_k \rangle = \sum_{\vec{R}} e^{i\vec{k} \cdot \vec{R}} \{ b_A \langle \varphi_A(\vec{r}) | \varphi_A(\vec{r}-\vec{R}) \rangle + b_B \langle \varphi_A(\vec{r}) | \varphi_B(\vec{r}-\vec{R}) \rangle \}$$

$$= \sum_{\vec{R}} e^{i\vec{k} \cdot \vec{R}} \{ b_A \int d^3r \varphi^*(\vec{r}) \varphi(\vec{r}-\vec{R})$$

$$+ b_B \int d^3r \varphi^*(\vec{r}) \varphi(\vec{r}-\vec{R}-\vec{d}) \}$$

We will assume that all overlaps are negligible except for nearest neighbors - recall that the nearest neighbors of A sites are B sites and vice versa.


So in the first term the only  $\vec{R}$  we consider is  $\vec{R} = 0$ .

In the 2nd term the only  $\vec{R}$  we consider are for  $\vec{R} + \vec{d} = \vec{J}, \vec{J}', \vec{J}''$  the vectors to the nearest neighbor i.e.  $\vec{R} = 0, \vec{R} = \vec{a}_1, -\vec{a}_2$ , and  $\vec{R} = -\vec{a}_2$

$$\langle \psi_A | \psi_k \rangle = b_A + b_B \int d^3r \phi^*(\vec{r}) \phi(\vec{r}-\vec{d}) \times [1 + e^{i\vec{k} \cdot (\vec{a}_1 - \vec{a}_2)} + e^{i\vec{k} \cdot (-\vec{a}_2)}]$$

where we used  $\int d^3r \phi^*(\vec{r}) \phi(\vec{r}) = 1$  by normalization  
 and  $\int d^3r \phi^*(\vec{r}) \phi(\vec{r}-\vec{d}) = \int d^3r \phi^*(\vec{r}) \phi(\vec{r}-\vec{d}')$   
 $= \int d^3r \phi^*(\vec{r}) \phi(\vec{r}-\vec{d}'')$

where the overlap integrals are all equal since  $\phi$  has rotational symmetry about the  $\hat{z}$  axis and

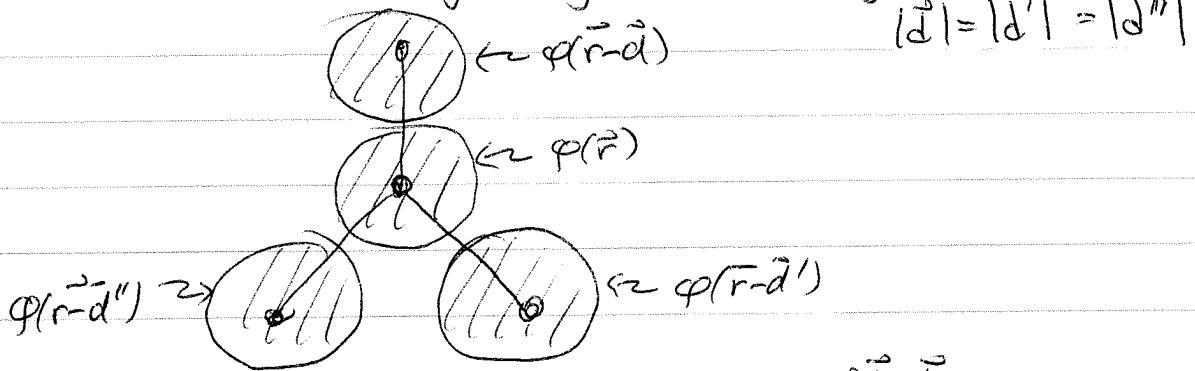

The term in  $[ \dots ]$  is just  $\sum_{\vec{R}} e^{i\vec{k} \cdot \vec{R}}$  over the set of  $\vec{R} = \{\vec{0}, \vec{a}_1, -\vec{a}_2, -\vec{a}_2\}$  that give the nearest neighbors  $\vec{J}, \vec{J}', \vec{J}''$ . The overlap integral is a common factor for all three terms.

Define  $\alpha = \int d^3r \varphi^*(\vec{r}) \varphi(\vec{r} - \vec{d})$

$$\begin{aligned} \text{then } \langle \varphi_A | \psi_k \rangle &= b_A + b_B \alpha [1 + e^{i\vec{k} \cdot \vec{a}_1} e^{-i\vec{k} \cdot \vec{a}_2} + e^{-i\vec{k} \cdot \vec{a}_2}] \\ &= b_A + b_B \alpha [1 + e^{-i\vec{k} \cdot \vec{a}_2} e^{i\vec{k} \cdot \vec{a}_1} (e^{i\frac{\vec{k} \cdot \vec{a}_1}{2}} + e^{-i\frac{\vec{k} \cdot \vec{a}_1}{2}})] \\ &= b_A + b_B \alpha [1 + e^{i\vec{k} \cdot (\frac{\vec{a}_1 - \vec{a}_2}{2})} 2 \cos(\vec{k} \cdot \frac{\vec{a}_1}{2})] \end{aligned}$$

$$\text{use } \vec{a}_1 = \alpha \hat{x}, \vec{a}_2 = \frac{\alpha}{2} \hat{x} + \frac{\sqrt{3}\alpha}{2} \hat{y}$$

$$\boxed{\langle \varphi_A | \psi_k \rangle = b_A + b_B \alpha [1 + e^{-i\frac{\sqrt{3}}{2} k_y \alpha} 2 \cos(k_x \alpha)]}$$

Similarly,

$$\begin{aligned} \langle \varphi_A | \Delta U | \psi_k \rangle &= \sum_{\vec{R}} e^{i\vec{k} \cdot \vec{R}} \left\{ b_A \int d^3r \varphi^*(\vec{r}) \Delta U(\vec{r}) \varphi(\vec{r} - \vec{R}) \right. \\ &\quad \left. + b_B \int d^3r \varphi^*(\vec{r}) \Delta U(\vec{r}) \varphi(\vec{r} - \vec{R} - \vec{d}) \right\} \end{aligned}$$

Again, keep only nearest neighbor overlaps, so  $\vec{R} = 0$  only in 1st term, and  $\vec{R} = \{\vec{0}, \vec{a}_1, -\vec{a}_1, \vec{a}_2, -\vec{a}_2\}$  in 2nd term.

Again, all the overlap integrals in 2nd term are equal

$$\begin{aligned} \int d^3r \varphi^*(\vec{r}) \Delta U(\vec{r}) \varphi(\vec{r} - \vec{d}) &= \int d^3r \varphi^*(\vec{r}) \Delta U(\vec{r}) \varphi(\vec{r} - \vec{d}') \\ &= \int d^3r \varphi^*(\vec{r}) \Delta U(\vec{r}) \varphi(\vec{r} - \vec{d}'') \end{aligned}$$

because  $\varphi(\vec{r})$  has rotational symmetry about  $\hat{z}$  axis  
and because  $\Delta U(\vec{r})$  has rotation by  $120^\circ$  symmetry  
about  $\hat{y}$  axis (maps  $\vec{d} \rightarrow \vec{d}' \rightarrow \vec{d}'' \rightarrow \vec{d}$ )

$$\text{Define } \beta = - \int d^3r \varphi^*(\vec{r}) \Delta U(\vec{r}) \varphi(\vec{r})$$

$$\gamma = - \int d^3r \varphi^*(\vec{r}) \Delta U(\vec{r}) \varphi(\vec{r} - \vec{d})$$

Then

$$\langle \varphi_A | \Delta U | \psi_k \rangle = -b_A \beta - b_B \gamma [1 + e^{-i\frac{\sqrt{3}}{2}k_y a} 2 \cos(k_x a)]$$

where  $[---]$  is the same factor from  $\sum_{\vec{k}} e^{i\vec{k} \cdot \vec{R}}$  that we had in  $\langle \varphi_A | \psi_k \rangle$ .

$$\text{Define } f(\vec{k}) = 1 + e^{-i\frac{\sqrt{3}}{2}k_y a} 2 \cos(k_x a)$$

$$\text{Our equation } \varepsilon_k \langle \varphi_A | \psi_k \rangle = E \langle \varphi_A | \psi_k \rangle + \langle \varphi_A | \Delta U | \psi_k \rangle$$

can now be written as:

$$0 = (\varepsilon_k - E) [b_A + b_B \alpha f(\vec{k})] + b_A \beta + b_B \gamma f(\vec{k})$$

$$(1) \quad \text{or} \quad (\varepsilon_k - E + \beta) b_A + [(\varepsilon_k - E) \alpha + \gamma] f(\vec{k}) b_B = 0$$

$$\text{We also need to consider } \langle \varphi_B | H | \psi_k \rangle$$

$$\Rightarrow \varepsilon_k \langle \varphi_B | \psi_k \rangle = E \langle \varphi_B | \psi_k \rangle + \langle \varphi_B | \Delta U | \psi_k \rangle$$

Repeating all the above steps, one arrives at:

$$(2) \quad (\varepsilon_k - E + \beta) b_B + [(\varepsilon_k - E) \alpha + \gamma] f^*(\vec{k}) b_A = 0.$$

Note  $\alpha, \beta, \gamma$  are real because for the  $p_z$  orbital  $\varphi^* = \varphi$  is real.

$f^*$  is complex conjugate of  $f$ .

Eqs (1) and (2) combine to give a set of two ~~two~~ homogeneous linear equations in two unknowns  $b_A, b_B$ . We can write them as:

$$M \cdot \begin{pmatrix} b_A \\ b_B \end{pmatrix} = 0$$

where  $M$  is the  $2 \times 2$  matrix

$$M = \begin{bmatrix} \epsilon_k - E + \beta & [(\epsilon_k - E)\alpha + \gamma] f(\vec{k}) \\ [(\epsilon_k - E)\alpha + \gamma] f^*(\vec{k}) & \epsilon_k - E + \beta \end{bmatrix}$$

there is a non-trivial solution for  $b_A, b_B$  only when  $\det M = 0$ . This condition gives a quadratic equation to solve for the two possible values of  $\epsilon(\vec{k})$ . Call these values  $\epsilon_{\pm}(\vec{k})$ . For each  $\vec{k}$  there are two solutions:  $\epsilon_-(\vec{k})$  is the  $\pi$  band,  $\epsilon_+(\vec{k})$  is the  $\pi^*$  band.

It is straightforward to solve the above quadratic for  $\epsilon_k$ . But to make things even simpler, let us assume that  $\alpha \ll \gamma$  and set the  $\alpha$  terms to zero:

$$\text{Note: } \begin{cases} \alpha \equiv \int d^3r \varphi(r) \varphi(\vec{r}-\vec{d}) \\ \gamma \equiv - \int d^3r \varphi^*(r) \Delta U(\vec{r}) \varphi(\vec{r}-\vec{d}) \end{cases}$$

Since  $\Delta U(\vec{r})$  is large at  $\vec{r}-\vec{d}$ , then roughly  $\varphi(\vec{r}-\vec{d}) \ll \Delta U(\vec{r}) \varphi(\vec{r}-\vec{d})$ , so indeed expect  $\alpha \ll \gamma$